

Manuscript Details

Manuscript number	JRE_2018_579_R2
Title	Selective microwave absorption in Nd ³⁺ substituted barium ferrite composites
Short title	Nd ³⁺ substituted barium ferrite composites
Article type	Full Length Article

Abstract

Microwave (MW) frequency based wireless communications and electronic devices became prospective due to several ramifications. To meet this need, a series of neodymium ions (Nd³⁺) substituted barium ferrite composites with composition (20)BaO:(80-x)Fe₂O₃:(x)Nd₂O₃ (0 ≤ x ≤ 3 mol%) was prepared at 1100 °C using solid-state reaction method. We evaluated the effect of various Nd³⁺ ions contents on the surface morphology, structure, and magnetic properties of the as-synthesized barium ferrite composites. Meanwhile, microwave reflection loss, complex permittivity, and permeability were determined using the transmission/reflection line method in the X-band (8-12 GHz). SEM image of the composites showed that the surface morphology consisted of rough and porous microstructures. XRD patterns of the un-doped composites revealed the existence of BaFe₁₂O₁₉ (hexagonal) and Fe_{21.333}O₃₂ (tetragonal) crystalline phases. Furthermore, a new hexagonal crystalline phase of Ba₆Nd₂Fe₄O₁₅ with the crystallite sizes between 15 and 67 nm was observed due to Nd³⁺ ions substitution in the composite. The saturation magnetization of the composite containing 2 mol% of Nd³⁺ did not exhibit any significant alteration compared to the one devoid of Nd³⁺. The complex relative permittivity and permeability of the achieved composites enriched in Ba₆Nd₂Fe₄O₁₅ and BaFe₂O₄ phases disclosed significant MW frequency dependence. The composites also displayed selective MW absorption in the X-band which could be useful for diverse applications.

Keywords	neodymium doping, barium ferrite composites, magnetic properties, porosity, MW reflection loss
Manuscript category	Magnetism and magnetic materials
Corresponding Author	Wahyu Widanarto
Corresponding Author's Institution	Universitas Jenderal Soedirman
Order of Authors	Wahyu Widanarto, Siti Khaeriyah, Sib Krishna Ghoshal, Candra Kurniawan, Mukhtar Effendi, Wahyu Tri Cahyanto

Submission Files Included in this PDF

File Name [File Type]

Cover Letter_NdBF.docx [Cover Letter]

Response_NdBF_R2.docx [Response to Reviewers]

Graphical Abstract_NdBF_R2.docx [Graphical Abstract]

Manuscript_NdBF_R2.docx [Manuscript File]

Figure_NdBF_R.docx [Figure]

To view all the submission files, including those not included in the PDF, click on the manuscript title on your EVISE Homepage, then click 'Download zip file'.

To
The Editor,
Journal of Rare Earths

Dear Sir / Madam,

We are submitting an Original Article entitled “**Selective microwave absorption in Nd³⁺ substituted barium ferrite composites**” authored by W. Widanarto, S. Khaeriyah, S. K. Ghoshal, C. Kurniawan, M. Effendi, W. T. Cahyanto, for the peer-review and publication in Journal of Rare Earths.

The article is our original research work and has been written as well as approved by all authors. It is not submitted to any other journal and under consideration for publication elsewhere, as well as no conflict of interest exists. If it is accepted, it will not be published elsewhere in the same form, in any language, without the written agreement of the publisher.

Best regards,

Wahyu Widanarto

Author Details:

W. Widanarto ^a, S. Khaeriyah ^a, S. K. Ghoshal ^b, C. Kurniawan ^c, M. Effendi ^a, W. T. Cahyanto ^a

^a Department of Physics, FMIPA, Universitas Jenderal Soedirman, Jl. dr. Soeparno 61 Purwokerto 53123, Indonesia

^b Department of Physics, AMORG, Faculty of Science, Universiti Teknologi Malaysia, Johor Bahru, Skudai 81310, Malaysia

^c Research Center for Physics, Indonesian Institute of Sciences (LIPI), Puspiptek Office Area, South Tangerang, Banten, Indonesia 15314

Corresponding Author:

W. Widanarto

E-mail address: wahyu.widanarto@unsoed.ac.id

The Editor

Journal of Rare Earth

Dear Sir,

Thanks to the reviewers for critical reading of the manuscript, providing invaluable comments and suggestions to modify it substantially. Please find attached herewith the responses to the reviewer's comments point by point on the paper. The authors gratefully acknowledge the invaluable comments and advise by the reviewer. The reviewer comments are presented in *italics* (BLACK) and the corresponding replies as standard text in BLUE below each comment. The newly added texts are highlighted in YELLOW in the revised manuscript.

Comments from the editors and reviewers:

Editor

I am very pleased to be able to tell you that the above paper has now been accepted for publication in Journal of Rare Earths. But before accepted, I have some minor questions and I would be grateful if you could address the points raised.

- 1) *Please note the fund project and number at the bottom of the first page, and the corresponding author (E-mail, telephone number) .*

Thanks for the advice. Please note that the fund project and number have been provided at the bottom of the first page of the manuscript.

- 2) *Please give a colorful graphic abstract at the end of the manuscript (TOC , figure +description).*

Thanks for the valuable suggestions. The graphical abstract has been provided at the end of the manuscript together with a short caption.

- 3) *The sencondary heading lines are necessary for "Results and Discussion"*

Thanks for the constructive advice. Please note that the secondary heading lines have been added in the revised manuscript

- 4) *Please fill the copyright transfer form and then upload it accompanying with the manuscript or send it to jrechina@263.net. The copyright transfer form is available at*

<http://www.re-journal.com> at column "JRE"

Thanks for the comments. Please note that the copyright form has been filled and uploaded.

5) Please cite 1-2 latest papers published on JRE in 2017-2018 in the references (if there have suitable papers), and submit the word file including all figures and tables after revision.

Thanks for the invaluable suggestions. Please note that two latest papers published in JRE have been cited.

6) Please note the reference format and check the Chinese authors' name (usually the abbreviation of Chinese author Yan Chunhua is like as Yan C H). if you are uncertain, please give full name for Chinese authors. If there are more than 6 authors, please list 6 author names + "et al". The format of the references is the followings:

1. Van der Geer J, Hanraads JAJ, Lupton RA. The art of writing a scientific article. *J Sci Commun.* 2000;163:51.

Reference to a book:

2. Strunk W Jr, White EB. *The Elements of Style*. 3rd ed. New York, NY: Macmillan; 1979.
Reference to a chapter in an edited book:

3. Mettam GR, Adams LB. How to prepare an electronic version of your article. In: Jones BS, Smith RZ, eds. *Introduction to the Electronic Age*. New York, NY: E- Publishing Inc; 1999:281.

Thanks for the constructive advice. Please note that we have changed the writing style of references as suggested.

7) In order to accelerate the online step after acceptance, please normalize all physical quantities and variables to italic. In addition, please use standard unit, such as "nm" instead of "Å", "Pa" instead of "atm".etc.

Please note that we have used the standard unit.

8) Please pay the publication charge and color fees with 700 dollars according to the enclosed alternative way and give receipt along with the revision or send to jrechina@263.net.

Thanks for the advice. Please note that the suggestions are well taken care.

The manuscript has been resubmitted for your kind perusal. We look forward for your positive response and acceptance of the revised manuscript.

Sincerely,

Wahyu Widanarto

Author Details:

W. Widanarto ^a, E. Ardenti ^a, S. K. Ghoshal ^b, C. Kurniawan ^c, M. Effendi ^a, W. T. Cahyanto ^a

^aDepartment of Physics, FMIPA, Universitas Jenderal Soedirman, Jl. dr. Soeparno 61 Purwokerto 53123, Indonesia

^bDepartment of Physics and Laser Centre, AMORG, Faculty of Science, Universiti Teknologi Malaysia, Johor Bahru, Skudai 81310, Malaysia

^cResearch Center for Physics, Indonesian Institute of Sciences (LIPI), Puspiptek Office Area, South Tangerang, Banten, Indonesia 15314


Corresponding Author:

W. Widanarto

E-mail address: wahyu.widanarto@unsoed.ac.id

Graphical abstract

The natural resonance frequency was altered due to Nd^{3+} substitution into BFs, thereby caused a shift in the MW reflection loss towards higher frequency.

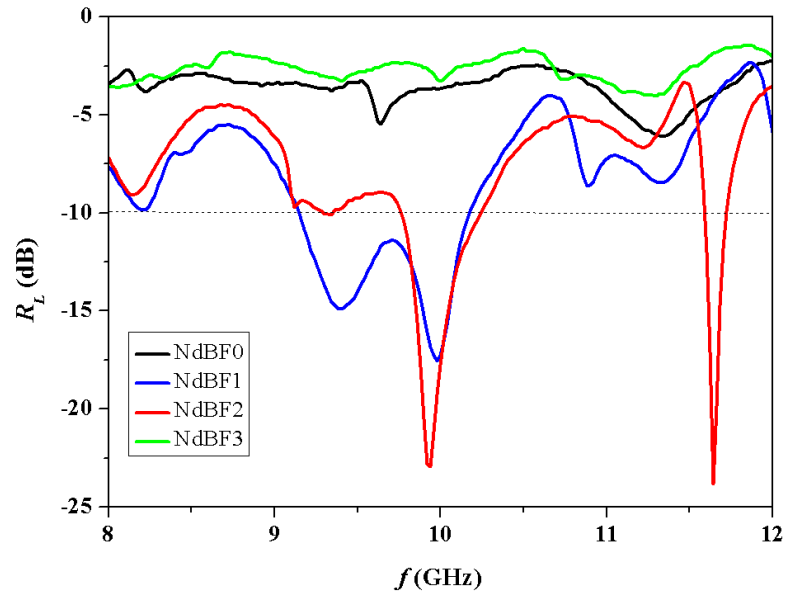

Selective microwave absorption in Nd³⁺ substituted barium ferrite composites

W. Widanarto ^{a,*}, S. Khaeriyah ^a, S. K. Ghoshal ^b, C. Kurniawan ^c, M. Effendi ^a, W. T. Cahyanto ^a

^a Department of Physics, FMIPA, Universitas Jenderal Soedirman, Jl. dr. Soeparno 61 Purwokerto 53123, Indonesia

^b Department of Physics and Laser Centre, AMORG, Faculty of Science, Universiti Teknologi Malaysia, Johor Bahru, Skudai 81310, Malaysia

^c Research Center for Physics, Indonesian Institute of Sciences (LIPI), Puspiptek Office Area, South Tangerang, Banten 15314, Indonesia

ABSTRACT

Microwave (MW) frequency based wireless communications and electronic devices became prospective due to several ramifications. To meet this need, a series of neodymium ions (Nd³⁺) substituted barium ferrite composites with composition (20)BaO:(80-*x*)Fe₂O₃:(*x*)Nd₂O₃ (0 ≤ *x* ≤ 3 mol%) was prepared at 1100 °C using solid-state reaction method. We evaluated the effect of various Nd³⁺ ions contents on the surface morphology, structure, and magnetic properties of the as-synthesized barium ferrite composites. Meanwhile, microwave reflection loss, complex permittivity, and permeability were determined using the transmission/reflection line method in the X-band (8–12 GHz). SEM image of the composites showed that the surface morphology consisted of rough and porous microstructures. XRD patterns of the un-doped composites revealed the existence of BaFe₁₂O₁₉ (hexagonal) and Fe_{21.333}O₃₂ (tetragonal) crystalline phases. Furthermore, a new hexagonal crystalline phase of Ba₆Nd₂Fe₄O₁₅ with the crystallite sizes between 15 and 67 nm was observed due to Nd³⁺ ions substitution in the composite. The saturation magnetization of the composite containing 2 mol% of Nd³⁺ did not exhibit any significant alteration compared to the one devoid of Nd³⁺. The complex relative permittivity and permeability of the achieved composites enriched in Ba₆Nd₂Fe₄O₁₅ and BaFe₂O₄ phases disclosed significant MW frequency dependence. The composites also displayed selective MW absorption in the X-band which could be useful for diverse applications.

Keywords: neodymium doping, barium ferrite composites, magnetic properties, porosity, MW reflection loss

1. Introduction

In recent times, wireless communications and electronic devices based on the microwave (MW) frequency in the range of 8-12 GHz (X-band) received focused attention, wherein dedicated efforts have been made to achieve the emission of such frequencies from a transmitter and radar. Materials required for such purposes must be capable in attenuating and dissipating the excess amount of electromagnetic energy in the form of thermal energy via magnetic and dielectric loss mechanisms [1]. Thus, novel magnetic materials (ferrites based) appropriate for absorbing the electromagnetic energy (MW) have continually been explored [2–10]. In this regard, barium hexaferrite (BHF) owing to its extremely high uniaxial magnetic anisotropy appeared an emergent MW absorbing material [3–5,11,12]. Thus, it became essential to optimize the MW absorption capacity of these ferrites in the X-band (8–12 GHz).

It was demonstrated that the natural resonance-frequencies, saturation magnetization, permeability, permittivity and magnetic field anisotropy of such ferrites could be altered by incorporating divalent or trivalent ions into the crystalline structures [13–15]. Consequently, the effects of electromagnetic interferences in these ferrites could be improved. Meanwhile, outstanding relaxation attributes of rare earth ions (REIs) as dopants inside the BHF have also been exploited to alter its magnetic and MW absorption characteristics [3,13,16–19]. Besides, BHF doped with REIs revealed weak coercive field (*H_c*) and low saturation magnetization (*M_s*)

which could be useful for the enhancement of MW absorption capacity [6,13,20,21]. Inspired by these innovations, we took an attempt to diminish the values of H_c and M_s of the prepared barium ferrite composites (BFCs), thereby enhancing the selective absorption of MW frequencies.

This communication reports the production and characterizations of new BFCs (hereafter referred as NdBFCs) wherein the Fe^{3+} ions in pure BHF were replaced by Nd^{3+} ions (at various concentration). Trivalent Nd^{3+} due to their compatible hexagonal lattice structure and excellent relaxational attributes were selected as doping agents (so-called substituent ions). Two types of composites (undoped and doped with Nd^{3+} ions) were synthesized via tailored solid-state reaction method. As-prepared composites were characterized using different analytical tools to determine the influence of Nd^{3+} ions on the microstructures, surface morphologies, magnetic characteristics, and MW reflection loss in the X-band. Achieved $\text{Ba}_6\text{Nd}_2\text{Fe}_4\text{O}_{15}$ and BaFe_2O_4 phases of the proposed BFCs were shown to be beneficial for sundry applications.

2. Materials and methods

Few BFCs (one without and three with Nd^{3+} ions doping) with the composition of $(20)\text{BaO}:(80-x)\text{Fe}_2\text{O}_3:(x)\text{Nd}_2\text{O}_3$, where $0 \leq x \leq 3$ mol% were prepared using modified solid-state reaction strategy. High purity powders (analytical grade) of BaCO_3 (Merck, 99%), Nd_2O_3 (Sigma Aldrich, 99%) and Fe_2O_3 (Sigma Aldrich, 99%) were used as preparatory materials to synthesize such BFCs. Furthermore, the BaCO_3 powder was calcined at 300 °C for an hour to remove the existed carbon element. Later, BaO powder was mixed gradually with Fe_2O_3 via annealing and sintering processes. Afterward, the Nd_2O_3 powder was added to the mixture and thoroughly mixed using a magnetic stirrer at the revolution speed of 700 rpm (rotation per minute) for two hours. Polyvinyl alcohol (PVA) was mixed and stirred continually until a sol was achieved. After that, the composite powder was compacted to produce pellets with the respective thickness and diameter of 1 mm and 1 cm [13]. Besides, some pellets of rectangular shape with a dimension of (2.5 cm × 1.5 cm × 0.2 cm) were obtained for additional characterizations. These pellets were further annealed at 800 °C for one hour and sintered at 1100 °C for five hours [22] before being cooled down naturally to room temperature. The achieved pellets were named as NdBF0, NdBF1, NdBF2, and NdBF3 based on their corresponding Nd^{3+} ions content of 0, 1, 2, and 3 mol%. Finally, the prepared composites were characterized at room temperature using different analytical techniques to determine the feasibility of achieving their selective MW absorption effectiveness in the X-band.

A scanning electron microscope (SEM, Hitachi SU 3500) equipped with energy dispersive X-ray (EDX, Horiba) was utilized to determine the surface morphologies, microstructures and elemental compositions of the synthesized NdBFCs [13,21,23]. The presence of crystalline phases in the studied NdBFCs was verified using X-ray diffraction measurement (XRD, SmartLab 3 kW) equipped with Cu-K α radiation of wavelength (λ) 0.1541874 nm. A vibrating sample magnetometer (VSM, Oxford 1.2H) was employed to examine the magnetic behavior of the studied composites. The scattering (S) parameters of the proposed composites were measured using a vector network analyzer (VNA, Advantest R3770) operated in the frequency range of 8–12 GHz. Additionally, the transmission/reflection line method was exploited to determine the MW reflection loss (R_L), the complex relative permittivity, and permeability.

3. Results and Discussion

3.1. Surface morphology and elemental traces

Fig. 1 displays the SEM images of all synthesized composites, wherein the surface morphology consisted of porous microstructures with roughness. Overall, the composites surface morphology and the distribution of particles size were influenced due to the Nd^{3+} ions

substitution into the crystalline lattices. At higher Nd^{3+} concentrations, the microstructure manifested two phases including the hexagonal grains of barium ferrite (dark color) and Nd-rich (bright color) regions. The microstructure of NdBF2 was more porous than the other samples. The mean grain size BFCs was shrunk from 2.5 to 1 μm with the increase in the Nd^{3+} ions content from 0 to 3 mol% accompanied by porosity enhancement. This enrichment in the porosity led to an improvement in the magnetic characteristics and MW-reflection loss [21]. Fig. 2 depicts the EDX spectra of all BFCs, confirming the appropriate elemental traces of O, Fe, Ba, and Nd wherein the inclusion of Nd in the composite caused an adjustment in the level of other elements (Table in the inset). Sample NdBF2 revealed the minimum traces of Nd (0.1 At.%), and NdBF3 exhibited the highest level of Nd (0.3 At.%).

Fig. 1. SEM micrographs of the as-synthesized NdBFCs.

Fig. 2. EDX spectrum of the as-synthesized NdBFCs

3.2. Crystalline structure and sizes

Fig. 3 illustrates the XRD patterns of the synthesized composites which comprised of several sharp peaks characteristics of different crystalline lattices. For the sample without Nd^{3+} substitution (NdBF0), all the observed peaks were assigned to the dominant hexagonal crystalline structure of $\text{BaFe}_{12}\text{O}_{19}$ which matched with the ICDD number 00-027-1029 with crystallographic parameters of $a = b = 0.5892 \text{ nm}$, $c = 2.3198 \text{ nm}$, $\alpha = \beta = 90^\circ$ and $\gamma = 120^\circ$. However, the peak appeared at 28.36° was allocated to the tetragonal crystal structure of $\text{Fe}_{21.333}\text{O}_{32}$ which was tallied with the ICDD numbers 01-076-1470. Furthermore, substitution of Fe^{3+} by Nd^{3+} ions (at 1 mol% of Nd_2O_3) in the barium ferrite lattice could produce a significant change in the in the crystal structure as verified by the XRD pattern of NdBF1. The emergence of two new peaks in NdBF1 corresponding to a primary phase of $\text{Ba}_6\text{Nd}_2\text{Fe}_4\text{O}_{15}$ and a secondary phase of $\text{BaFe}_{18}\text{O}_{27}$ were clearly disclosed. The occurrences of sharp XRD peaks were allotted to the hexagonal lattice of $\text{Ba}_6\text{Nd}_2\text{Fe}_4\text{O}_{15}$ (matched with the ICDD number 01-079-2141) with $a = b = 1.1815 \text{ nm}$, $c = 0.7078 \text{ nm}$, $\alpha = \beta = 90^\circ$ and $\gamma = 120^\circ$. Moreover, the peak centered at 32.17° was endorsed to the hexagonal crystalline lattice of $\text{BaFe}_{18}\text{O}_{27}$ (matched with the ICDD number 01-075-0406). The inclusion of 2 mol% of Nd_2O_3 (sample NdBF2) into the BFCs could transform the crystalline phase from hexagonal $\text{BaFe}_{18}\text{O}_{27}$ to orthorhombic BaFe_2O_4 structure (matched with the ICDD number 01-077-2337). Meanwhile, further addition of Nd_2O_3 up to 3 mol% in the BFCs (sample NdBF3) led to an alteration in the XRD peak position of BaFe_2O_4 without significant variations in the phase and structure. It was affirmed that the replacement of Fe^{3+} by Nd^{3+} ions in the studied BFCs could generate a new primary hexagonal crystalline phase of $\text{Ba}_6\text{Nd}_2\text{Fe}_4\text{O}_{15}$. Widening of the diffraction peaks for all as-synthesized NdBFCs is credited to the nano-crystalline size and lattice strain [24,25]. The crystallite sizes of the studied $\text{Ba}_6\text{Nd}_2\text{Fe}_4\text{O}_{15}$ (calculated using the Debye-Scherrer's equation) were ranged from 15 to 67 nm.

Fig. 3. XRD patterns of all as-synthesized NdBFCs

3.3. Magnetic Properties

Fig. 4 depicts the magnetization (M) concerning the applied field (H) of all the studied barium ferrites without and with Nd^{3+} ions substitution. The composite without containing Nd^{3+} ions (NdBF0) revealed that the saturation magnetization (M_s), remanence magnetization (M_r), and coercivity field (H_c) were 16.36 emu/g, 11.82 emu/g, and 0.24 T, respectively. The overall magnetic behavior of the composite (NdBF1), except for the M_s did not significantly change due to addition 1 mol% of Nd_2O_3 . The Inclusion 2 mol% of Nd_2O_3 into the composite (NdBF2) did

not affect the value of M_s . However, incorporation 3 mol% of Nd_2O_3 into the composite (NdBF3) could lead to an increase in the value of M_s comparable to NdBF1, which was ascribed to the enhanced porosity of the barium ferrite surface. It was argued that the occurrence of such excessive porosity could isolate the magnetic domain walls, leading to natural polarization of the unpaired magnetic spins in the presence of an external applied magnetic field. The magnetic hysteresis loop of NdBF0 coincided with NdBF2. Similarly, the magnetic hysteresis loop of NdBF1 was overlapped with NdBF3. Thus, it was established that such pair ferrites (NdBF0 and NdBF2 as well as NdBF1 and NdBF3) had almost identical magnetic properties. Disclosure of such narrow hysteresis loops (loop-gap area) indeed confirmed the soft magnetic character of the proposed BFCs. On top, the studied composites failed to display the complete saturation magnetization because of the presence of antimagnetic materials such as BaFe_2O_4 and $\text{Fe}_{21.333}\text{O}_{32}$. The underlying development of the non-magnetic phase because of a sintering procedure at high temperature is likewise in charge of altering M_s [25,26].

Fig. 4. Hysteresis loops of the studied NdBFCs

3.4. Complex relative permittivity and permeability

Fig. 5a shows the frequency-dependent complex relative permittivity (ϵ_r) for all composites in the X-band. The real (ϵ') and imaginary (ϵ'') components of the permittivity of the prepared composites aroused from the intrinsic electric dipole polarization were strongly depended on the MW frequencies [27]. Actually, the real part of the permittivity signified the energy stored in the material from an external electric field [28]. The real part of the permittivity revealed three prominent resonance peaks around 8.7, 10.0, and 11.8 GHz, indicating the storage of energy in the composites from the electric field. Nevertheless, the lack of stored energy could be observed at other MW frequencies. Meanwhile, the imaginary part of the permittivity signified the dielectric loss factor, denoting the energy dissipation capacity of the material. The appearance of the resonance peaks in the ϵ' spectrum was trailed by the disappearance of the resonance peaks in the ϵ'' spectra [13]. It was affirmed that the proposed composites presented the best energy storage performance around 11.6 GHz, wherein the absorbed energy was consumed for the magnetic domain wall motion.

Fig. 5b illustrates the frequency dependent complex relative permeability for all composites in the X-band. The real part of the permeability (μ') exhibited three significant resonance peaks around 8.5, 9.3, and 11.0 GHz, demonstrating the magnetic energy storage capacity of the composites. Alternatively, the imaginary part of the permeability (μ'') revealed the magnetic loss factor around 8.2, 9.0, and 10.5 GHz, which was allocated to the natural resonance frequency f_r [13]. Besides, the magnetic loss factor was increased at the resonance frequency. It was observed that the substitution of Fe^{3+} in the BFCs by Nd^{3+} at varied concentrations caused the frequency shift. This disclosure was attributed to the emergence of different phase and porosity in the composites. The imaginary part of the permeability plays an important role in the microwave absorbing property of hexaferrites [29] that related to the relaxation of domain wall resonance [30].

Fig. 5. Frequency-dependent complex relative (a) permittivity and (b) permeability for all NdBFCs

3.5. Microwave reflection loss

Fig. 6 represents the variation in the reflection loss (R_L) of all prepared BFCs as a function of applied MW frequency (f). The NdBF0 and NdBF3 composites revealed a similar trend in the R_L pattern which comprised of two weak absorption bands with values above -10 dB.

Meanwhile, the NdBF1 specimen exhibited R_L value below -10 dB at frequencies range of 9.14 to 10.18 GHz. Besides, NdBF2 composite disclosed two prominent absorption bands centered around 9.94 and 11.64 GHz with R_L values of -22.94 and -23.82 dB, respectively. All the observed spectral bands showed a significant shift with varying contents of Nd^{3+} ions with the bandwidth of less than 1 dB. In short, the microwave absorption capacity of the proposed BFCs was improved due to Nd^{3+} ions substitution assisted enhanced porosity in the structure that in turn could confine the MW. Consequently, the Nd^{3+} ions substitution into the BFs could change the magnetocrystalline anisotropy direction of the composites, leading to an alteration of the natural resonance frequency. This alteration could finally cause a shift of the MW reflection loss to high-frequency zone as revealed by NdBF2. Interestingly enough, the doped composites enriched in $\text{Ba}_6\text{Nd}_2\text{Fe}_4\text{O}_{15}$ and BaFe_2O_4 phases could absorb microwaves selectively in the X-band.

Fig. 6. Frequency-dependent MW reflection loss of all the proposed NdBFCs

4. Conclusion

Synthesis and room temperature characterization of some new hexagonal barium ferrite composites with Nd^{3+} ions substitution was reported. An appropriate amount of chemical constituents were gradually mixed to prepare these composites following solid-state reaction route. The proposed BFCs revealed the excellent capacity of MW absorption in the X-band. EDX spectra revealed the right elemental compositions of the prepared BFCs and presence of Nd in the structures. The surface morphology, structure, magnetic properties and MW absorption ability of the prepared BFCs were strongly influenced because of the inclusion of Nd^{3+} ions into the crystalline lattice. The XRD pattern disclosed the formation of new crystalline phases of $\text{Ba}_6\text{Nd}_2\text{Fe}_4\text{O}_{15}$ and BaFe_2O_4 due to the incorporation of Nd^{3+} ions into the BFCs structure. SEM images of the studied BFCs exhibited highly rough and porous surface morphology. At 2 mol% of Nd^{3+} ions, the saturation magnetization of the BFCs displayed insignificant alteration. The complex relative permittivity and permeability of the studied BFCs were found to depend appreciably on the MW frequencies. Furthermore, the achieved low reflection loss at 9.94, and 11.64 GHz frequencies with selective MW absorption shown by the proposed BFCs may be advantageous for diverse device applications in the X-band.

Acknowledgments

Authors are grateful to Universitas Jenderal Soedirman, Kemenristekdikti Indonesia, and UTM Malaysia for financial assistance.

REFERENCES

- [1] Kim MS, Koh JG, Microwave-absorbing characteristics of NiCoZn ferrite prepared by using a co-precipitation method, J. Korean Phys. Soc. 2008;53:737.
- [2] Yuan CL, Tuo YS, Microwave adsorption of $\text{Sr}(\text{MnTi})_x\text{Fe}_{12-2x}\text{O}_{19}$ particles, J. Magn. Magn. Mater. 2013;342:47.
- [3] Sun C, Sun K, Chui P, Microwave absorption properties of Ce-substituted M-type barium ferrite, J. Magn. Magn. Mater. 2012;324: 802.
- [4] Changshun D, Xin W, Peiheng Z, Tao L, Jianliang X, Longjiang D, Microwave magnetic and absorption properties of M-type ferrite $\text{BaCo}_x\text{Ti}_x\text{Fe}_{12-2x}\text{O}_{19}$ in the Ka band, J. Magn. Magn. Mater. 2014;354:340.
- [5] Salman S, Afghahi SSS, Jafarian M, Atassi Y, Microstructural and magnetic studies on $\text{BaMg}_x\text{Zn}_x\text{X}_{2x}\text{Fe}_{12-4x}\text{O}_{19}$ ($\text{X}=\text{Zr}, \text{Ce}, \text{Sn}$) prepared via mechanical activation method to act as a microwave absorber in X-band, J. Magn. Magn. Mater. 2016;406:184.

- [6] Ziqiang Q, Shunkang P, Jilei X, Lichun C, Qingrong Y, Peihao L, Magnetic and microwave absorption properties of La-Nd-Fe alloys, *J. Magn. Magn. Mater.* 2017;423:197.
- [7] Taurino R, et al., New ceramic materials from MSWI bottom ash obtained by an innovative microwave-assisted sintering process, *J. Eur. Ceram. Soc.* 2017;37:323.
- [8] Gu L, Liuying W, Zhihong Y, Renbing W, Synthesis of iron-based hexagonal microflakes for strong microwave attenuation, *J. Alloys Compd.* 2017;718: 46.
- [9] Bibi M, et al, Microwaves absorbing characteristics of metal ferrite/multiwall carbon nanotubes nanocomposites in X-band, *Compos. Part B Eng.* 2017; 114:139.
- [10] Jialiang L, Shunkang P, Lichun C, Peihao L, Yu H, Junqing C, Electromagnetic and microwave absorption properties of Er-Ho-Fe alloys Jialiang, *J. Rare Earths.* 2018;36:715.
- [11] Yue L, Tingjin W, Ying L, Xiaojie L, Ying L, Mechanism for Synthesizing Barium Hexagonal Ferrite by Sol-Gel Method, *Adv. Mater. Res.* 2012;549:105.
- [12] Bierlich S, Gellersen F, Jacob A, Töpfer J, Low-temperature sintering and magnetic properties of Sc- and In-substituted M-type hexagonal barium ferrites for microwave applications, *Mater. Res. Bull.* 2017;86:19.
- [13] Widanarto W, Amirudin F, Ghoshal SK, Effendi M, Cahyanto WT, Structural and magnetic properties of La³⁺ substituted barium–natural nanoferrites as microwave absorber in X-band, *J. Magn. Magn. Mater.* 2017;426: 483.
- [14] Kanna RR, Lenin N, Sakthipandi K, Sivabharathy M, Impact of lanthanum on structural, optical, dielectric and magnetic properties of Mn_{1-x}Cu_xFe_{1.85}La_{0.15}O₄ spinel nanoferrites, *Ceram. Int.* 2017;43:15868.
- [15] Bhongale SR, Ingawale HR, Shinde TJ, Vasambekar PN, Effect of Nd³⁺ Substitution on Structural and Magnetic Properties of Mg-Cd Ferrites Synthesized by Microwave Sintering Technique, *J. Rare Earths.* 2018;36:390.
- [16] Ahmed MA, Okasha N, Kersh RM, Influence of rare-earth ions on the structure and magnetic properties of barium W-type hexaferrite, *J. Magn. Magn. Mater.* 2008;320:1146.
- [17] Guozhu S, Zheng X, Yi L, Absorbing properties and structural design of microwave absorbers based on W-type La-doped ferrite and carbon fiber composites, *J. Magn. Magn. Mater.* 2006;301:325.
- [18] Wang J, Zhang H, Bai S, Chen K, Zhang C, Microwave absorbing properties of rare-earth elements substituted W-type barium ferrite, *J. Magn. Magn. Mater.* 2007;312:310.
- [19] Lianwen D, Li D, Kesheng Z, Shengxiang H, Zhaowen H, Bingchu Y, Electromagnetic properties and microwave absorption of W-type hexagonal ferrites doped with La³⁺, *J. Magn. Magn. Mater.* 2011;323:1895.
- [20] Seyyed Afghahi SS, Jafarian M, Salehi M, Atassi Y, Improvement of the performance of microwave X band absorbers based on pure and doped Ba-hexaferrite, *J. Magn. Magn. Mater.* 2017;421:340.
- [21] Widanarto W., Ardenti E., Ghoshal SK., Kurniawan C., Effendi M., Cahyanto WT., Significant reduction of saturation magnetization and microwave-reflection loss in barium-natural ferrite via Nd³⁺ substitution, *J. Magn. Magn. Mater.* 2018;456:288.
- [22] Widanarto W, Jandra M, Ghoshal SK, Effendi M, Cahyanto WT., BaCO₃ mediated modifications in structural and magnetic properties of natural nanoferrites, *J. Phys. Chem. Solids.* 2015;79:78.
- [23] Widanarto W, Rahayu FM, Ghoshal SK, Effendi M, Cahyanto WT., Impact of ZnO substitution on magnetic response and microwave absorption capability of strontium-natural nanoferrites, *Results Phys.* 2015;5:253.
- [24] Vinila VS, et al, XRD Studies on Nano Crystalline Ceramic Superconductor PbSrCaCuO at Different Treating Temperatures, *Cryst. Struct. Theory Appl.* 2014;3:1.

- [25] Dabagh S, Ati AA, Rosnan RM, Zare S, Othaman Z, Effect of Cu-Al substitution on the structural and magnetic properties of Co ferrites, *Mater. Sci. Semicond. Process.* 2015;33:1.
- [26] Ewais EMM, Hessien MM, El-Geassy A.-HA, In-Situ Synthesis of Magnetic Mn-Zn Ferrite Ceramic Object by Solid State Reaction, *J. Aust. Ceram. Soc.* 2008;44:57.
- [27] Lin W, Hongtao Y, Xiaohu R, Guangliang X, Magnetic and microwave absorption properties of $\text{BaMn}_x\text{Co}_{1-x}\text{TiFe}_{10}\text{O}_{19}$, *J. Alloys Compd.* 2014;588:212.
- [28] Das CK, Bhattacharya P, Kalra SS, Graphene and MWCNT: Potential Candidate for Microwave Absorbing Materials, *J. Mater. Sci. Res.* 2012;1:126.
- [29] Wang L, Huang Q, Mu L, Zhang Q, Influence of Sm^{3+} Substitution on Microwave Magnetic Performance of Barium Hexaferrites, *J. Rare Earths.* 2007;25:216.
- [30] Wang L, Lin P, Pan S, Zhou H, Microwave absorbing properties of NdFeCo magnetic powder, *J. Rare Earths.* 2012;30:529.

Fig. 1.

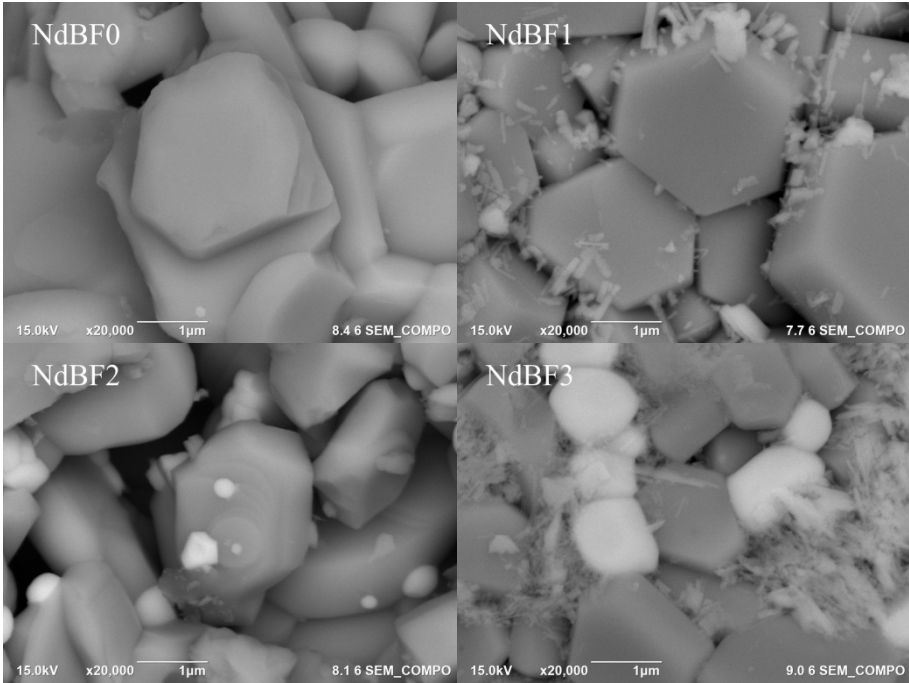


Fig. 2.

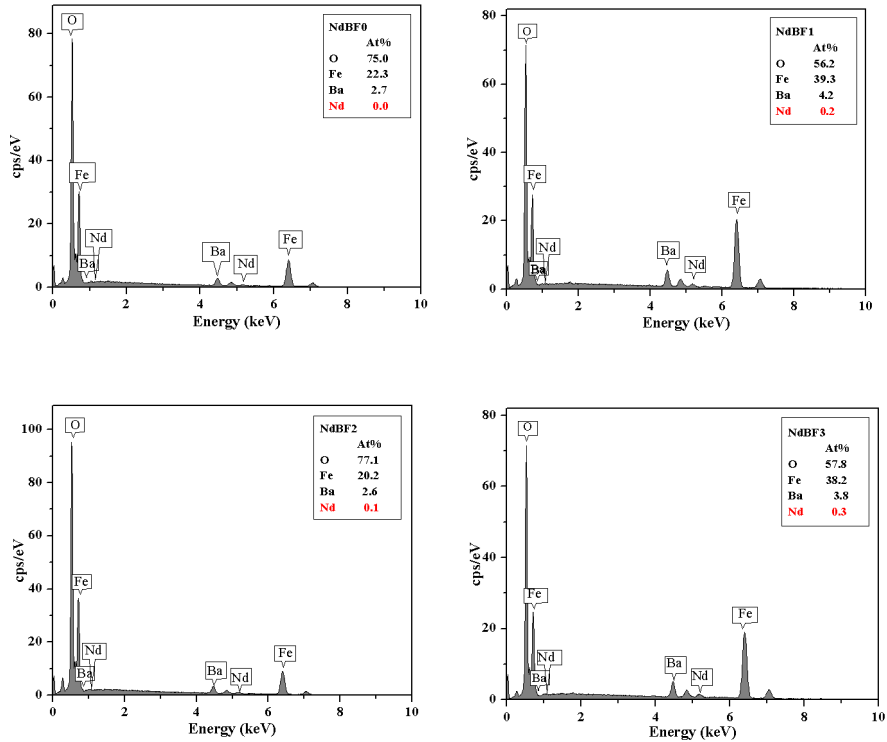


Fig. 3.

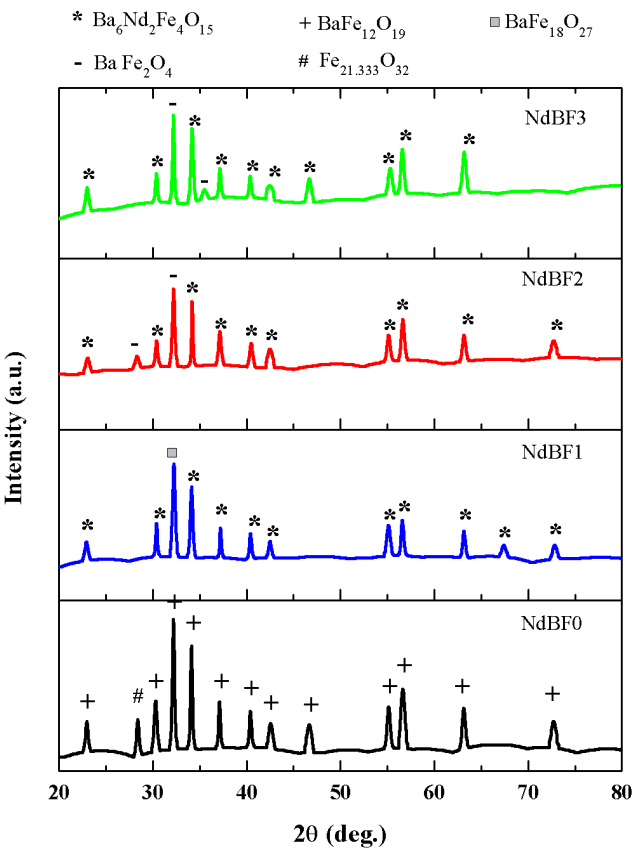


Fig. 4.

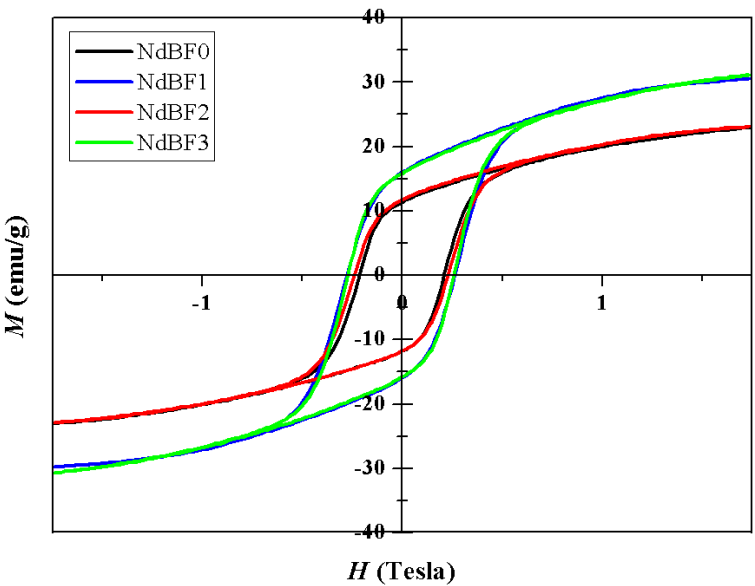


Fig. 5.

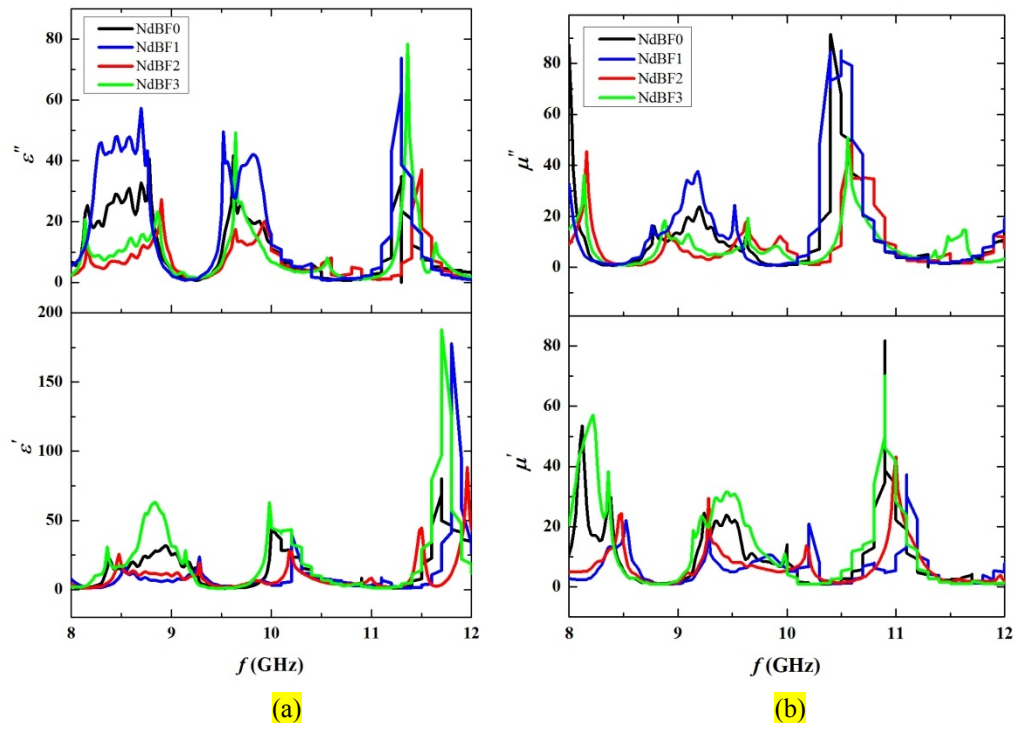


Fig. 6.

